

International Conference on Space Optics—ICSO 2008

Toulouse, France

14–17 October 2008

Edited by Josiane Costeraste, Errico Armandillo, and Nikos Karafolas



Optical characterization of infrared telluride glass fibers for space use

A.J. Faber

L.K. Cheng

W. L.M. Gielesen

C. Boussard-Plédel

et al.



International Conference on Space Optics — ICSO 2008, edited by Josiane Costeraste, Errico Armandillo, Nikos Karafolas, Proc. of SPIE Vol. 10566, 105660X · © 2008 ESA and CNES
CCC code: 0277-786X/17/\$18 · doi: 10.1117/12.2308263

Proc. of SPIE Vol. 10566 105660X-1

OPTICAL CHARACTERIZATION OF INFRARED TELLURIDE GLASS FIBERS FOR SPACE USE

A.J. Faber⁽¹⁾, L.K. Cheng⁽¹⁾, W. L.M. Gielesen⁽¹⁾, C. Boussard-Plédel⁽²⁾,
S. Maurugeon⁽²⁾, B. Bureau⁽²⁾, X.H. Zhang⁽²⁾, J. Lucas⁽²⁾, J. Pereira Do Carmo⁽³⁾

⁽¹⁾TNO Science and Industry, P.O. Box 6235, 5600 HE Eindhoven, The Netherlands, Email: anne-jans.faber@tno.nl

⁽²⁾University of Rennes, France, ⁽³⁾ESA-ESTEC, Noordwijk, The Netherlands

ABSTRACT

High Tellurium (Te) content chalcogenide glass fibers are considered as candidates for single mode waveguides in the upper wavelength range (10 – 20 μm) of the DARWIN mission. In this paper two methods for IR optical characterization of the Te glass fibers are presented, including (1) a broadband spectral technique using an FTIR spectrophotometer and (2) a CO₂ laser set-up for measuring the fiber attenuation at 10.6 μm . In both methods the optical attenuation (in dB/m) of experimental mono index Te glass fibers of around 500 μm diameter has been determined by applying the fiber cut-back technique. Some typical results of both methods for a few different types of high Te-glass fibers will be shown.

Since Te-glasses are semiconducting materials, the optical properties of Te-glass fibers strongly depend on temperature. Preliminary low temperature measuring results confirm the beneficial effect of cooling on the transmission of high Te glass fibers.

1. INTRODUCTION

An important measuring technique under study for the DARWIN planet finding mission, is nulling interferometry [1,2]. The main goal of this mission is to identify terrestrial planets, orbiting around nearby stars and capable of having an atmosphere, so possibly supporting life. The principle of nulling interferometry is the destructive interference of the intense light emitted by a central star, thus enabling the detection of the weak infrared emission lines of the orbiting planet. This technique requires a perfect wavefront of the light beams to be combined in the interferometer. By using a single mode waveguide before detection, higher order modes are filtered and a virtually perfect plane wavefront is obtained

Since the main emission lines of the relevant atmospheric components like CO₂, O₃ and water vapour are all in the mid IR, from 4 – 20 μm , the envisaged single mode waveguides must be transparent in this spectral range.

Step index, Te-As-Se (TAS) chalcogenide glass fibers are considered to be suitable waveguides for the lower

DARWIN wavelength range from 4 – 10 μm [1,2]. In this paper, high Te content chalcogenide glasses are proposed as candidates for waveguides in the upper (10 - 20 μm) DARWIN wavelength range. Typical results of optical characterization on unclad, mono-index fibers of high Te glass compositions are presented and discussed here.

2. EXPERIMENTAL

2.1 Preparation of unclad high Te glass fibers

Unclad (mono index) high Te content fibers were manufactured from the following chemical glass compositions:

- TeGeGal
- TeGeI
- TeGeSe

Using special raw materials preparation, chemical purification and glass melting procedures [3], glass rods of about 9 mm diameter and about 10 cm length were manufactured. These glass rods were drawn to mono index fibers (ϕ from 400 – 550 μm), using a special fiber drawing machine, described previously [4]. Several meters of three TeGeGal type mono-index fibers (two non-purified ϕ 400 μm and one purified ϕ 400 $\mu\text{m}/\phi$ 520 μm) were drawn, showing a good surface quality, free of defects or crystallization (see Fig. 1.).



Fig. 1. Mono-index TeGeGal fiber on drum

Similar preparation procedures were used to manufacture fibers of more than 10 meters length from the TeGeI and TeGeSe glass compositions.

2.2 Infrared optical characterization methods

(1) Broadband spectral set-up

An experimental set-up was built for measuring the spectral loss of the unclad (mono-index) Te glass fibers in the region 4 – 20 μm by the fiber cut-back technique. The components of this set-up are described in Table 1.

Table 1 Components of broadband spectral set-up

Component	Specification
Light source	Ceramic coil, emitting from 1.5 – 55 μm
Detector	MIRTGS (1 – 45 μm) with CsI window
Detection instrument	Perkin Elmer 2000 FTIR spectrophotometer with CsI beamsplitter and CsI window
Fiber holder	Aluminium substrate with V-groove on alignment stage
Optics	Mirrors for focussing the light into the fiber
Pinhole	0.9 mm diameter for defining the focus point at the input of the fiber

Some pictures of the set-up are presented in Fig. 2.

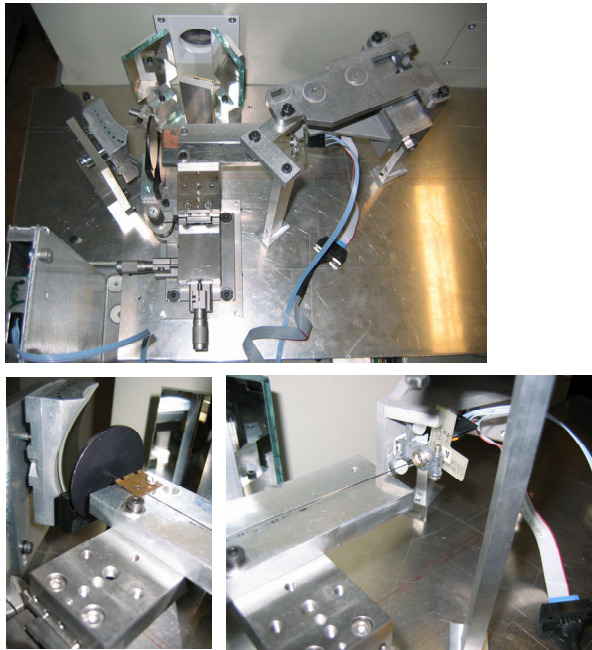


Fig. 2. Top view of broadband spectral set-up (top) with details, showing the fiber (on Al substrate) in front of the pinhole (bottom left) and the output of the fiber close to the detector window (bottom right)

(2) CO₂ laser set-up

The attenuation measurements at 10.6 μm using the cut-back method are performed with a pulsed CO₂ laser (SYNRAD J48-1SW). The maximum output power is 10W, the beam size is about 3 mm and the pulse

frequency is 5 kHz. The output optical power can be tuned by changing the duty cycle. The set-up is sketched in Fig. 3.

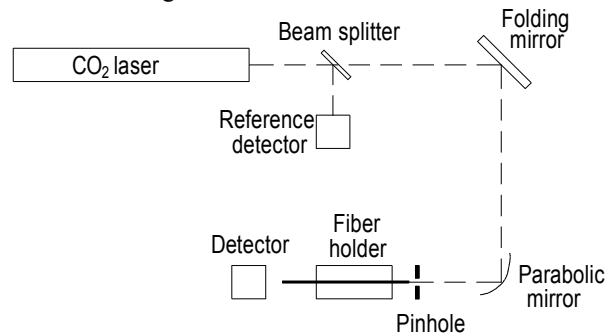


Fig. 3. Pulsed CO₂ laser set-up for fiber attenuation measurements at 10.6 μm

3. RESULTS OF OPTICAL ATTENUATION MEASUREMENTS ON TE-GLASS FIBERS

3.1 Attenuation at room temperature

Spectral attenuation of TeGeGaI fibers

The transmission of two TeGeGaI fiber samples, approximately 5 cm long, was measured using the broadband spectral set-up. One fiber sample was prepared from an untreated glass and another sample from a similar glass composition, after an additional chemical purification procedure to remove (oxygen) impurities.

The corresponding spectra are presented in Fig. 4.

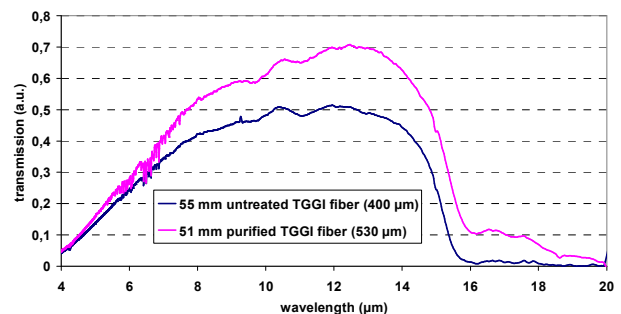


Fig. 4. Comparison of spectral transmission of a 5 cm fiber of purified and non-purified (untreated) TeGeGaI mono-index fiber

It can be seen in Fig. 4 that the TeGeGaI fiber has the highest transmission in the 12 – 13 μm region. Besides, part of the absorption of the TeGeGaI fiber in the region 15 – 20 μm is extrinsic, probably due to oxygen related impurities. By the application of proper

purification methods, the transmission in the region 15 – 20 μm can be increased.

Next, the spectral attenuation of a 9 cm long sample of the purified TeGeGal fiber was determined by cutting back this fiber piece in 3 steps to about 3 cm.

The measured average spectral attenuation is presented in Fig. 5.

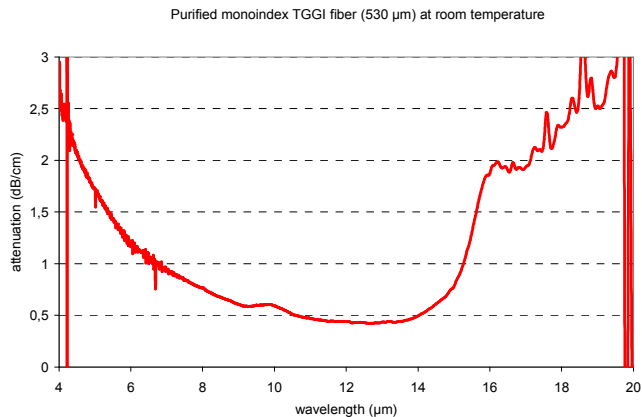


Fig. 5. Averaged spectral attenuation (dB/cm) of a purified TeGeGal fiber at room temperature determined by fiber cut-back method

A minimum in the attenuation of 0.4 dB/cm was found between 12 and 13 μm . The attenuation between 16 and 20 μm increases from a value around 1.5 dB/cm to 3 dB/cm.

Although the measured values for the spectral loss are still relatively high, these results prove that the purified TeGeGal fiber transmits light in the region between 15 and 20 μm through short fiber samples. This performance can probably be improved by advanced glass manufacturing processing and improved purification methods.

Attenuation of high Te fibers at 10.6 μm

The attenuation at 10.6 μm of fiber samples of about 50 cm long of the glass types TeGeGal, TeGeI and TeGeSe was determined by cutting back these fibers in many steps to about 10 cm. After each cut the transmitted light intensity through the remaining fiber length was measured.

The results of the fiber cut-back measurements with the CO₂ laser set-up are summarized in Table 2.

Table 2 Attenuation at 10.6 μm of different high Te-glass fiber types (unclad), made from purified glasses

Fiber type	Attenuation (dB/cm)
TeGeGal	0.46
TeGeI	0.17
TeGeSe	0.10

The measured loss value at 10.6 μm of 0.46 dB/cm for the TeGeGal glass fiber corresponds reasonably well with the measured values between 10 and 11 μm in Fig. 5. Apparently, the optical loss at the CO₂ laser wavelength (10.6 μm) of the glass fiber types TeGeI and particularly TeGeSe is considerably lower.

This observation was confirmed by other spectral measurements, not reported here, which showed that the TeGeSe glass fibers have a minimum attenuation between 10 and 11 μm , so slightly shifted to shorter wavelengths compared to TeGeGal fibers. The origin of the differences in the optical loss between the different fiber types (intrinsic/extrinsic absorptions, glass quality, crystals in the fiber, etc.) is still under study.

3.2 Attenuation at low temperatures

In order to simulate temperature conditions in space, a qualitative experiment was carried out on a 135 mm long TeGeGal-fiber, cooled by liquid N₂, using the broadband FTIR set-up of Fig. 2.. The spectrum measured at low temperature was compared to the spectrum of the same fiber at room temperature and the ratio of both curves was calculated, as shown in Fig. 6.

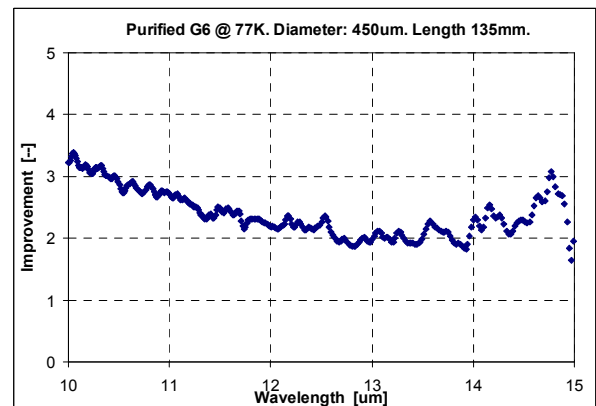


Fig. 6. Factor of improvement in transmission of a TeGeGal fiber at liquid nitrogen compared to room temperature

It can be seen in Fig. 6 that the transmission of the TeGeGal fiber increases at low temperature and that the improvement due to cooling is wavelength dependent. The minimum improvement in optical transmission at liquid N₂ temperature is a factor of 2 at about 13 μm .

4. CONCLUDING REMARKS

The optical loss of different types of high Te content, unclad glass fibers was measured by the fiber cut-back

method, using a broadband FTIR set-up and a single wavelength CO₂ laser set-up. Optical attenuation values down to 0.1 – 0.5 dB/cm were measured, depending on glass type, glass preparation/purification processes and IR wavelength. The TeGeSe glass fiber samples appeared to have the lowest loss of 0.1 dB/cm at 10.6 μm.

Since high Te-glasses are semiconducting materials, the optical properties of Te-glass fibers strongly depend on temperature. Preliminary low temperature measurements showed an improvement of the Te glass fiber transmission at liquid nitrogen temperatures of minimum a factor 2.

Taking into account the optical transmission results, it is concluded that high Te-glass fibers are realistic candidates for satisfying the DARWIN waveguide requirements in the upper wavelength range from 10 – 20 μm.

5. REFERENCES

1. A.J. Faber, L.K. Cheng, W.L.M. Gielesen, C. Boussard-Plédel, P. Houizot, S. Danto, J. Lucas and J.Pereira Do Carmo, "Single-mode chalcogenide glass fiber as wavefront filter for the DARWIN planet finding mission", *Proc. 6th Int. Conf. on Space Optics*, ESTEC, Noordwijk, The Netherlands, 27 - 30 June 2006
2. P. Houizot, C. Boussard-Plédel, A.J. Faber, L.K. Cheng, B. Bruno, P.A. Van Nijnatten, W.L.M. Gielesen, J. Pereira do Carmo, J. Lucas, "Infrared single mode chalcogenide glass fiber for space", *OPTICS EXPRESS*, Vol.15, No.19, (17 September 2007)
3. A. Wilhelm, C. Boussard-Plédel, Q. Coulombier, J. Lucas, B. Bureau, P. Lucas, 'Development of far-infrared-transmitting Te based glasses suitable for carbon dioxide detection and space optics', *Advanced Materials*, 19, (2007), 3796–3800
4. S. Hocdé, C. Boussard-Plédel, G. Fonteneau, J. Lucas, 'Chalcogen based glasses for IR fiber chemical sensors', *Solid State Sciences*, 3 (3), (2001), 279